

PRODUCTION OF ACTIVATED CARBON FROM RICE HUSK AND ITS PROXIMATE ANALYSIS

Md. Niamul Bari^{*1}, Farzana Yasmin Muna², Mumtahina Rahnuma³, Md. Iquebal Hossain⁴

¹Professor, Rajshahi University of Engineering & Technology, Bangladesh, e-mail: niamulbari@gmail.com

²Graduate student, Rajshahi University of Engineering & Technology, Bangladesh, e-mail:

farzanayasminmuna@gmail.com

³Undergraduate student, Rajshahi University of Engineering & Technology, Bangladesh, e-mail:

rahnumamouli66@gmail.com

⁴Superintending Engineer, Barind Multipurpose Development Authority, Rajshahi, Bangladesh, e-mail:

iquebal_hossain@yahoo.com

***Corresponding Author**

ABSTRACT

With the increasing population, the pollution of the environmental elements is increasing day by day. Activated Carbon (AC) is solid, carbonaceous, non-hazardous, and highly porous complex compound and due to its adsorption property, this is widely used in the purification of various elements of the environment such as air, water, chemical, metal, etc. So, the enthusiasm in the production of activated carbon by the utilization of cheap agricultural and industrial wastes is growing rapidly. This study has been carried out to demonstrate the attempt of utilizing Rice Husk (RH) as a precursor material for the production of activated carbon. In this study, for the production of ACs, the carbonization temperature was taken at 500°C and 700°C, as well as the effect of temperature in the production process, was evaluated. Activation is done by the chemical activation process while impregnating with the activation agent potassium hydroxide (KOH) at different ratios. The impregnation ratio of RHC: KOH were 1:0.25, 1:0.5, 1:1 and 1:2 by weight. All the samples were activated in the muffle furnace at a temperature of 500°C for 1 hr. This study shows the feasibility of activated carbon from agricultural by-products at a cost-effective production process for achieving the minimum product requirements. Characteristics such as volatile matter, carbon content, yield, and activation burn-off were determined in this research. All in all, lower carbonization temperature (500°C) gives better results in all parameters. The increasing ratio also decreased the volatile substances and comparatively better yield obtained at less burning. While choosing only one ratio for both temperatures, the 1:1 ratio displayed better performance as further increases of agent decreased the product yield.

Keywords: Rice husk, rice husk carbon, activated carbon, impregnation, proximate analysis

1. INTRODUCTION

Activated carbon (AC) is a form of carbon processed to have small, low volume pores that increase the surface area which is usually derived from charcoal. AC is a solid, tasteless, anamorphic black carbonaceous, non-hazardous, highly porous compound that has a complex structure made of carbon atoms with internal surface area ranging between 300-3500 m²/gm. This surface area is related to its internal atom structure that gives activated carbon the adsorbent property (Arnelli, et al., 2019) and is composed of hierarchical pores named micro, meso and macropores with diameters <2nm, 2–50nm and >50 nm respectively. AC are characterized by their surface area, high micro-porosity and adsorption capacity, enabling them to be utilized as an effective adsorbent in the water treatment process (Poinern, et al., 2015) and also for the removal of organic and inorganic pollutants (Pak, et al., 2016; Gokce and Aktas, 2014; Korotta and Santhasivan, 2017). Application of ACs are most preferred not only due to their highly developed internal surface area, porosity and consequently a large adsorption capacity, but also due to their simplicity in design, and ease of operation (Bhatnagar and Sillanpaa, 2017).

The demand for using ACs is increasing day by day because of enhanced awareness about environmental protection. However, due to costly equipment and its maintenance, the production of commercial ACs are still very expensive for costly natural precursors such as wood, coal, etc. Therefore, much research has prompted finding lower production costs and eco-friendly alternative materials which can be transformed into low-cost AC. Previous researches illustrated that agricultural wastes can be suitable sources of raw material for the production of activated carbon including animal bones (Cechinel, et al., 2014), waste bamboo cums (Wang, 2012), mangosteen peel, sludge (Bjorklund and Li, 2017), waste tires (Betancur, et al., 2009), durian shell, coconut shell (Iriarte-Velasco, et al., 2008), rice husks (Chen et al., 2011; Foo and Hameed, 2011; Liou and Wu, 2009), nuts, sugar cane bagasse (Goncalves, et al., 2016), rubberwood, molasses (Goncalves, et al., 2016), and orange peel (Hashemian, et al., 2014). Some factors such as cost, availability, ease of activation, renewability, inorganic content and carbon yield influence the choice of raw materials for the production of AC. Rice husk (RH) is an agricultural waste that has no commercial interest which usually ends up either being openly dumped or burnt instead of recycling. In Bangladesh, it is a major by-product of the rice milling industry. Moreover, globally the production of RH is over 120 million metric tons (Abbas and Santosh, 2010) and about 20% of the paddy weight is RH (Kumagai, et al., 2007). Production of activated carbon from rice husk can increase the value of this agricultural waste and reduce the disposal cost at the same time can provide a cheap alternative to existing commercial activated carbon.

Rice husk has high percentages of carbon as contains lots of cellulose, hemicellulose and lignin. The surface of the carbon is tremendously increased by the removal of hydrocarbon through the physical change called activation. The synthesis of AC comprises two steps. Firstly, the dried RH is carbonized at lower temperatures (<800°C) to produce black char. Secondly, AC is prepared at higher temperatures either by physical activation (Alvarez, et al., 2014) or by chemical activation (Isoda, et al., 2014). The physical process requires the presence of steam or carbon dioxide (CO_2) and the chemical process requires activating agents e.g. potassium hydroxide (KOH), sodium hydroxide (NaOH), zinc chloride ($ZnCl_2$) and phosphoric acid (H_3PO_4) followed by activation in an inert atmosphere (Kalderis, et al., 2008). Apparently, for recommended lower temperature for Chemical, the development of porous structure outcomes better as the porous framework can destroy at higher temperatures.

The characteristic of AC depends on its activation method and its Physico-chemical properties (Lua and Guo, 2000). Physical properties such as moisture content, volatile matters, fixed carbon, ash residues, iodine value, methylene blue value, pH value, conductivity (Sm-1), bulk density, specific gravity, decolorizing power and percentage of carbon (C), hydrogen (H_2), oxygen (O_2) value. Many studies have been carried out with potential and locally available rice husk as a raw material for low-cost adsorbent material and it is proved that activated carbon derived from rice husk shows better performance than industrial-grade activated carbon for decolorization of textile water (Rahman et al., 2013). However, a carbonization temperature-oriented study along with activating chemical ratio has not been much explored. This concern served as a motivation for our research. In this study, rice husk as a precursor material for the production of AC is proposed. However, an approach is done in this research of considering varying carbonization temperature along with impregnation ratio during AC production and carrying out a comparative study between products through proximate analysis.

2. METHODOLOGY

In this study, rice husk was used as the main raw material and potassium hydroxide (KOH) worked as an activating agent. The Carbonization temperature and impregnation ratio changed throughout the whole process and other factors such as activation time, activation temperature carbonization time, and amount of rice husk carbon were kept fixed. There was two carbonization temperature used, 500°C and 700°C respectively. Each carbonized rice husk was further impregnated with KOH in four ratios of 1:0.25, 1:0.50, 1:1 and 1:2 (w/w). Also, some characterization was executed with the weight recorded at every stage with a digital balance. The process is shown with a flow diagram in Figure 1.

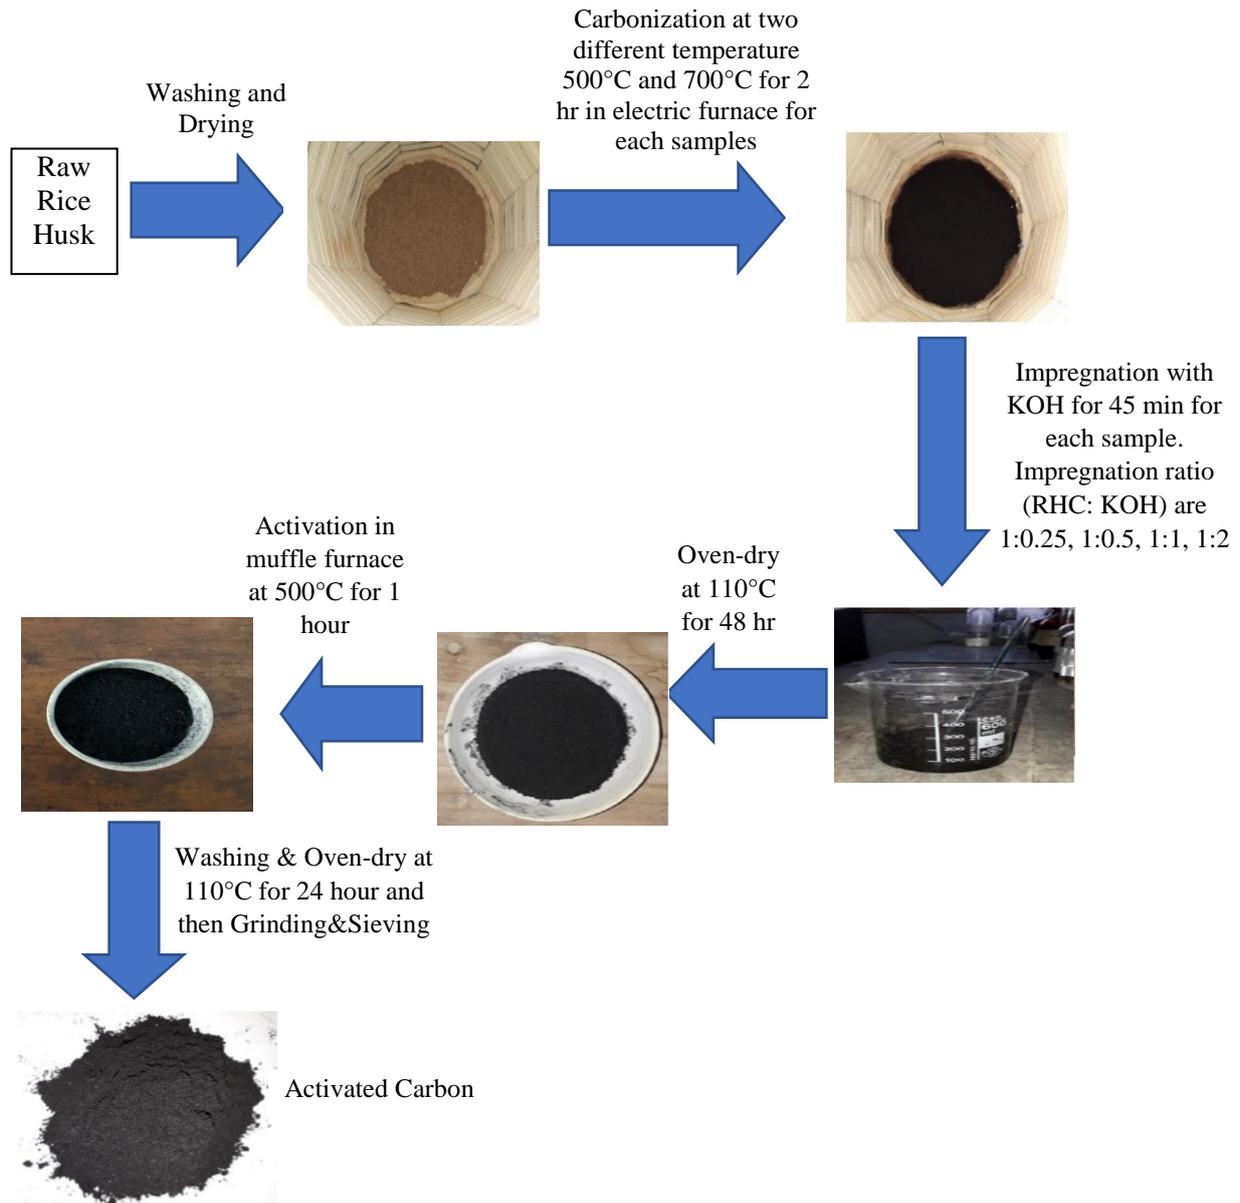


Figure 1: Flow diagram of ACs production procedure

2.1 Preparation of Carbon from Rice Husk

Locally available rice husk was collected from Nabil Auto Rice Mill (unit-2), Rajshahi. Raw rice husk was washed with distilled water several times so that dirt and other substances could be removed initially from RH. Then it was placed in the oven at 60°C until the rice husk got completely dried. This washed and oven-dried rice husk was used for the preparation of rice husk carbon. That rice husk was then placed into the electric furnace (Model: SHTL-233). The temperature was fixed at 500°C and 700°C for burning and kept for about 2 hours. After cooling the electric furnace, the rice husk carbon was obtained. The prepared carbon is shown in the following Figure 2.



Figure 2: Rice husk & Rice husk carbon

2.2 Activation of Rice Husk Carbon

In this experiment, potassium hydroxide (KOH) solution was used as activating agent. For each temperature (500°C and 700°C) four ratios of rice husk carbon and potassium hydroxide solid were taken. The ratio of rice husk carbon and potassium hydroxide were maintained at 1:0.25, 1:0.50, 1:1 and 1:2 by weight. Between four samples after 700°C carbonizations, for two samples, 20 gm and 40 gm of KOH solid were taken to mix with 20 grams of rice husk carbon in each to obtain the ratio of 1:1 and 1:2 respectively. For this, KOH solid had to mixed with distilled water to make a solution of 100 ml and then through stirring and gradually pouring the 20 gm carbon. The amount of distilled water for two solution were more for ratio 1:1 (carbon:agent) as naturally KOH solid release liquid in open environment. Other remaining two samples were prepared by mixing 15 gm of carbon with 7.5 gm and 3.75 gm of KOH for preparing the ratio of C: KOH as 1:0.5 and 1:0.25 respectively and in the same manner 100 ml solution obtained and then carbon were mixed thoroughly. Same procedure followed for preparing the other four samples from carbonized at 500°C derived carbon mixed with KOH in each sample was contained 20gm, where the amount of KOH used as 5gm, 10gm, 20 gm and 40 gm for preparing ratio of 1:0.25, 1:0.5, 1:1, 1:2 (w/w) respectively. The samples were stirred for about 1 hour and then placed in the oven at 120°C for 48 hours. The oven-dried activated samples were put into the muffle furnace (Barnstead Thermolyne 47900 Furnace) for further activation at 500°C for 1 hour.

After activation in the muffle furnace, the activated carbon was washed with distilled water several times till the activating agent washed properly and the sample got a neutral pH value. Then these all eight samples were oven-dried at 110°C for 24 hours. After which all samples were grounded by using pestle mortar and passed through 0.075mm sieve and collected the produced activated carbon. All the samples were stored in air-tight boxes for further analysis. The sample of produced AC can be shown below in Figure 3.



Figure 3:Final Activated Carbon

2.3 Proximate Analysis

Proximate analysis was done to determine the carbon content, volatile matters, activation burn-off, and product yield, for separate cases. The methods of these analyses are briefly described in the following sections.

Carbon content

Carbon content could be determined from the difference of weights of samples before and after burning in the electric furnace as ash-free. The following equation is used to calculate the carbon content where w_1 is the weight of dried rice husk and w_2 is the weight of produced ash-free carbon after burning in the furnace.

$$\text{Carbon content (\%)} = \frac{w_2}{w_1} \times 100 \text{----- (1)}$$

Ash Content

Ash content of rice husk was determined as a percentage of rice husk from the weight of ash produced after burning at 550°C for 1 hr in the muffle furnace. The weight of produced ash is w_3 and the following equation is used to calculate.

$$\text{Ash content (\%)} = \frac{w_3}{w_1} \times 100 \text{----- (2)}$$

Volatile matter

The mass losses are due to the release of volatile matters in a continual carbonization process with an increase in temperature. Therefore, the content of volatile matter can easily be determined from the difference in weight of carbon and ash from the weight of rice husk taken for carbonization. The calculation is expressed as equation 3.

$$\text{Volatile matter (\%)} = \frac{w_1 - w_2 - w_3}{w_1} \times 100 \text{----- (3)}$$

Activation burn-off

The loss of mass during the activation process varied with the variation of temperature (Saka, 2012). Burn-off refers to the loss of weight during the activation process. It can be determined with the difference between the weight of char with activation reagent and weight of product after activation. It can be expressed as equation 4 (Rhaman, et al., 2015).

$$\text{Activation burn-off}(\%) = \frac{(w_4+w_5)-w_6}{w_4} \times 100 \text{ ----- (4)}$$

Where, w₄, w₅ and w₆ are the weight of carbon before activation, the weight of activation reagent and the weight of carbon after activation, respectively.

Yield of AC

Yield is the percentage of the final product with respect to the original raw material. It could be determined from the mass of AC produced finally and the mass of rice husk used for the production. The yield of activated carbon was estimated with equation 5. The weight of the final product of activated carbon after washing for complete removal of residual alkali and drying is denoted as w₇ and the weight of rice husk used is w₁.

$$\text{Yield of activated carbon}(\%) = \frac{w_7}{w_1} \times 100 \text{ ----- (5)}$$

3. RESULTS AND DISCUSSIONS

The produced activated carbon from rice husk was characterized with proximate analysis and determined the yield, carbon content, volatile matter, and activation burn-off. The obtained results are presented in Table 1.

Table 1: Activated Carbon Characterization

Carbonization Temperature	Carbon Content (%)	Volatile Matter (%)	Ash Content (%)
500°C	14.96	63.22	21.82
700°C	14.28	63.81	21.91

The results demonstrate that there is no significant effect of temperature on the production of carbon from rice husk and it is around 15% of the raw material. Similarly, while comparing between samples, it can be noticed that the percentages of volatile matter of rice husk obtained at 500°C and 700°C are the same (63.22% and 63.81%) which means that volatile matter has been completely removed at or below the temperature of 500°C. As volatile matter works as an obstruction for the activating agent, the complete removal of the volatile matter before activation (during the production of carbon) from the raw material indicates an excellent property of precursor material for the production of activated carbon. Furthermore, the ash content obtained was 21.82% and 21.91% at 500°C and 700°C, respectively. Rhaman, et al. (2015) obtained fixed carbon 14.40% and Sharath, et al. (2017) obtained 20.99% from rice husk. Therefore, a comparable quantity of carbon was produced in this study.

The mass decreased during activation was called activation burn-off and this varied with varying activation temperature (Rhaman, et al., 2015). The extent of activation of the char depends on the extent of burn-off. The yield of activated carbon and activation burn-off for different ratios of the activating agent at a temperature of 500°C and 700°C are presented in Figure 4. It is observed that the activation burn-off is increasing with the increase of activation agent and temperature. On the other hand, the yield of activated carbon decreased with the increase of activation agent and temperature. The yield of activated carbon decreased with the increase of temperature due to the increase of activation burn-off

with an increase of temperature. Furthermore, the yield strongly depends on the amount of alkali used (Rhaman, et al., 2015).

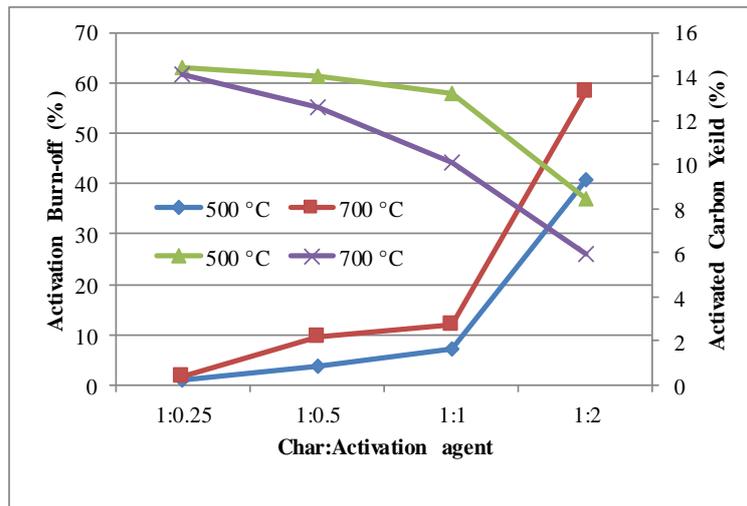


Figure 4: The relations of activation and yield of activated carbon with the ratio of activation agent

Chang, et al. (2000) showed that the higher temperature char has a more developed pore structure. Pore development in the carbon would enhance the surface area and pore volume of the activated carbon by promoting the diffusion of activating agent molecules into the pores and thereby increasing the agent-carbon reaction via acid hydrolysis processes which would then create more pores (Hong et al., n.d.). Here below can be seen typical SEM image of rice husk, rice husk char and activated carbon in (a), (b) and (c) section of Figure 5 respectively presented by (Hanum et al., 2017).

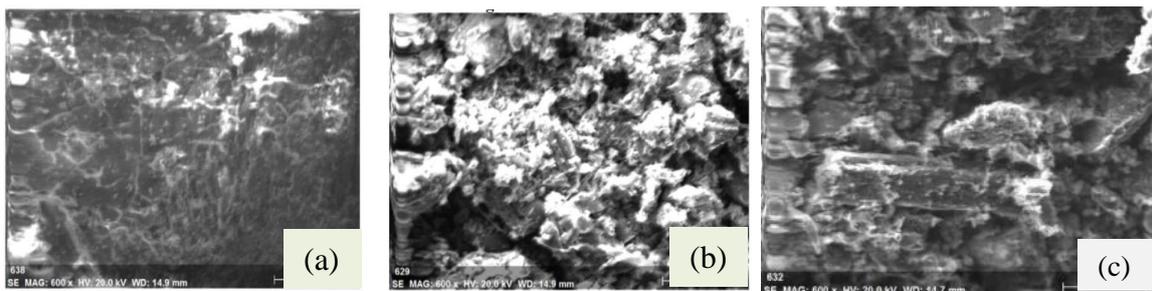


Figure 5: (a) SEM of rice husk, (b) SEM of rice husk char & (c) SEM of activated carbon (Hanum et al., 2017)

Also, high temperatures can reduce the activation time of the same burn-off. Thus, a higher temperature can overcome the drawbacks of a longer period of activation time required to attain a larger surface area and offer a higher potential to produce activated carbon of greater adsorption capacity. The higher burn-off develops microporosity and widens the micropore by removing the obstructing agent from the char (Carrott et al. 2003). It is due to the more reduction of volatile substances at higher temperatures and with higher content of activation agent. However, a higher amount of alkali used for the activation to obtain a high surface area with increased porosity might not be economical sometimes considering the production and material costs.

4. CONCLUSIONS

In this study, rice husk-based activated carbon is produced with different alkali ratios (1:0.25, 1:0.5, 1:1 and 1:2 (w/w)) in two different carbonization temperatures and an approach of proximate characterization

is done. The study showed the percentage of volatile matter is nearly the same for both temperatures. Although activation burn off increases with the temperature, the yield of activated carbon decreases. Here, carbonization at 700°C exhibits a better surface area, but the yield of activated carbon is lower. Again, higher alkali content can increase the porosity in activated carbon resulting in uneconomical production. Therefore, activated carbon produced with 1:1 of char carbonized at 500°C and activation agent would be profitable considering the activation burn-off, yeildof activated carbon, carbon content and volatile matter.

ACKNOWLEDGEMENT

The authors acknowledge the contribution of another co-author SwakharSaha who passed away shortly after the preparation of the manuscript.

REFERENCES

- Abbas, A. and Santosh, A. (2010). Global Potential of Rice Husk as a Renewable Feedstock for Ethanol Biofuel Production. Volume -03, DO- 10.1007/s12155-010-9088-0.
- Alveraz, J., Lopez, G., Amutio, M., Bilbao, J., and Olazar, M. (2014). Upgrading the rice husk char obtained by flash pyrolysis for the production of amorphous silica and high quality activated carbon. *Bioresource Technology*, 170, 132–137. <https://doi.org/10.1016/j.biortech.2014.07.073>.
- Arnelli, U.H.H.P, Fandi, N.C. and Yayuk, A. (2019). Use of microwave radiation for activating carbon from rice husk using ZnCl₂ activator. *Jornal kimia sains dan Aplikasi* 22(6):283-291
- Betancur, M., Martínez, J.D., and Murillo, R. (2009). Production of activated carbon by waste tire thermochemical degradation with CO₂. *Journal of Hazardous Materials*, 168(2–3), 882–887. <https://doi.org/10.1016/j.jhazmat.2009.02.167>
- Bhatnagar, A., and Sillanpää, M. (2017). Removal of natural organic matter (NOM) and its constituents from water by adsorption – A review. *Chemosphere*, 166, 497–510. <https://doi.org/http://dx.doi.org/10.1016/j.chemosphere.2016.09.098>
- Bjorklund, K., and Li, L. Y. (2017). Adsorption of organic stormwater pollutants onto activated carbon from sewage sludge. *Journal of Environmental Management*, 197, 490–497. <https://doi.org/10.1016/j.jenvman.2017.04.011>
- Carrott, P.J.M., Carrott, M.M.L.R., Mourão, P.A.M. and Lima, R.P. (2003). Preparation of Activated Carbons from Cork by Physical Activation in Carbon Dioxide. *Adsorption Science & Technology* Vol. 21 No. 7, 669-681.
- Cechinel, M.A.P., Ulson De Souza, S.M.A.G., and Ulson De Souza, A.A. (2014). Study of lead (II) adsorption onto activated carbon originating from cow bone. *Journal of CleanerProduction*, 65, 342–349. <https://doi.org/10.1016/j.jclepro.2013.08.020>
- Chang, C.F., Chang, C.Y. and Tsai, W.T. (2000). Effects of Burn-off and Activation Temperature on Preparation of Activated Carbon from Corn Cob Agrowaste by CO₂ and Steam. *Journal of Colloid and Interface Science* 232, 45–49 (2000) doi:10.1006/jcis.2000.7171
- Chen, Y., Zhu, Y., Wang, Z., Li, Y., Wang, L., Ding, L. and Guo, Y. (2011). Application studies of activated carbon derived from rice husks produced by chemical-thermal process - A review. *Advances in Colloid and Interface Science*, 163(1),39–52. <https://doi.org/10.1016/j.cis.2011.01.006>.
- Foo, K. Y. and Hameed, B.H. (2011). Utilization of rice husks as a feedstock for preparation of activated carbon by microwave induced KOH and K₂CO₃ activation. *Bioresource Technology*, 102(20), 9814–9817. <https://doi.org/10.1016/j.biortech.2011.07.102>
- Gokce, Y. and Aktas, Z. (2014). - Nitric Acid Modification of Activated Carbon Produced from Waste Tea and Adsorption of Methylene Blue and Phenol. *Applied Surface Science* 313 (2014) 352-359.
- Gonçalves, G. da C., Pereira, N. C., and Veit, M. T. (2016). Production of bio-oil and activated carbon from sugarcane bagasse and molasses. *Biomass and Bioenergy*, 85, 178–186. <https://doi.org/10.1016/j.biombioe.2015.12.013>

- Hanum, F., Bani, O., & Wirani, L. I. (2017). Characterization of activated carbon from rice husk by hcl activation and its application for lead (Pb) removal in car battery wastewater. *IOP Conference Series: Materials Science and Engineering*, 180(1). <https://doi.org/10.1088/1757-899X/180/1/012151>
- Hashemian, S., Salari, K., and Yazdi, Z. A. (2014). Preparation of activated carbon from agricultural wastes (almond shell and orange peel) for adsorption of 2-pic from aqueous solution. *Journal of Industrial and Engineering Chemistry*, 20(4), 1892-1900. <https://doi.org/10.1016/j.jiec.2013.09.009>.
- Hong, B., Xue, G., Weng, L., & Guo, X. (n.d.). *PRETREATMENT OF MOSO BAMBOO WITH DILUTE PHOSPHORIC ACID*.
- Iriarte-Velasco, U., Álvarez-Urriarte, J.I., Chimeno-Alanís, N., and González-Velasco, J.R. (2008). Natural Organic Matter Adsorption onto Granular Activated Carbons: Implications in the Molecular Weight and Disinfection Byproducts Formation. *Industrial & Engineering Chemistry Research*, 47, 7868–7876. <https://doi.org/DOI: 10.1021/ie800912y>
- Isoda, N., Rodrigues, R., Silva, A., Gonçalves, M., Mandelli, D., Figueiredo, F.C.A., and Carvalho, W.A. (2014). Optimization of preparation conditions of activated carbon from agriculture waste utilizing factorial design. *Powder Technology*, 256, 175-181. <https://doi.org/10.1016/j.powtec.2014.02.029>
- Kalderis, D., Bethanis, S., Paraskeva, P. and Diamadopoulos, E. (2008), Production of activated carbon from bagasse and rice husk by single stage chemical activation method at low retention times, *Bioresour Technol* 99(15): 6809-6816.
- Korotta-Gamage, S.M. and Sathasivan, A. (2017). - A review: Potential and challenges of biologically activated carbon to remove natural organic matter in drinking water purification process. *Chemosphere* 167 (2017) 120-138.
- Kumagai, S., Noguchi, Y., Kurimoto, Y., and Takeda, K. (2007). Oil adsorbent produced by the carbonization of rice husks. *Waste Management*, 27(4), 554–561. <https://doi.org/10.1016/j.wasman.2006.04.006>
- Liou, T.H. and Wu, S.J. (2009). Characteristics of microporous/mesoporous carbons prepared from rice husk under base- and acid-treated conditions. *Journal of Hazardous Materials*, 171(1–3), 693–703. <https://doi.org/10.1016/j.jhazmat.2009.06.056>
- Lua, A.C. and Guo, J. (2000). Activated carbon prepared from oil palm stone by one-step CO₂ activation for gaseous pollutant removal. 38(7), 1089–1097. doi:10.1016/s0008-6223(99)00231-6
- Pak, S.H., Jeon, M.J. and Jeon, J.W. (2016). -Study of sulfuric acid treatment of activated carbon used to enhance mixed VOC removal. *International Biodeterioration & Biodegradation* 113 (2016) 1-6
- Poinern, Kamariya, S. and Pandya, J. (2016). Preparation and Characterization of Activated Carbon from Agricultural Waste, Peanut Shell by Chemical Activation. *International Journal of Trend in Research and Development*, Volume 3(3), ISSN: 2394-9333.
- Rahman, M. M., HamidulBari, Q., Mohammad, N., Ahsan, A., Sobuz, H. R., & Alhaz Uddin, Md. (2013). Characterization of Rice Husk Carbon Produced through Simple Technology. *Advances in Materials Science and Applications*, 2(1), 25–30. <https://doi.org/10.5963/amsa0201003>.
- Rhaman, M.T., Haque, M.A., Rouf, M.A., Siddique, M.A.B. and Islam, M.S. (2015). Preparation and characterization of activated carbon & amorphous silica from rice husk. *Bangladesh J. Sci. Ind. Res.* 50(4), 263-270.
- Saka, C. (2012). BET, TG–DTG, FT-IR, SEM, iodine number analysis and preparation of activated carbon from acorn shell by chemical activation with ZnCl₂. *Journal of Analytical and Applied Pyrolysis* 95 (2012) 21–24.
- Sharath, D., Ezana, J. and Shamil, Z. (2017). Production of Activated Carbon from Solid Waste Rice Peel (Husk) using Chemical Activation. *Jr. of Industrial Pollution Control* 33(2) (2017) pp 1132-1139.
- Wang, L. (2012). Application of activated carbon derived from “waste” bamboo culms for the adsorption of azo disperse dye: Kinetic, equilibrium and thermodynamic studies. *Journal of Environmental Management*, 102, 79–87.